

# Technical Data Sheet

Farapol Jam Chemical Indus. Co.

## FARAPOL O 136

**Product Description** Farapol O 136 is an Unsaturated Polyester Resin-based Orthophthalic Anhydride and standard Glycols, dissolved in and cross-linked with Styrene Monomer. The product is medium reactive, flame-retardant base polymer, corrosion resistant and excellent fiberglass wet out.

**Applications and Use** This resin has flame resistance without additives, so this resin is a suitable option in composite production processes where flame resistance is required. This resin is designed to be manufactured using hand lay-up, spray up and mold grating processes. This resin has good compatibility with aluminum trihydrate ATH.

**Certificates and Approvals** Farapol Jam Chemical Industrial Company carries out the production, quality control, and distribution of this resin in compliance with ISO 9001, 14001, 45001, 10002, 10004, 10015, and 17065 standards.


### Typical Liquid Resin Properties

<i>Property @ 25 °C</i>	<i>Unit</i>	<i>Specification</i>	<i>Method</i>
Viscosity Brookfield <sup>1</sup>	cps	430 - 480	ISO 2555
Acid Value	mgKOH/g	Max 30	ASTM D 1639
Solid Content	%	66 - 69	ISO 3251
Color	Gardner	Max 2	ASTM D 1544
Specific Gravity	relative	1.20-1.30	ISO 2811
Gel Time <sup>2</sup>	minute	15 - 20	ASTM D 2471

- 1) Gel Time and viscosity can be adjusted as per customer requirements.
- 2) Gel time measuring formulation used: (Cobalt Octoate Farapol C 9010 1%- 1.0 phr, Akperox A60 1.0 phr).

### Flame Test Result on Clear Cast Mold

<i>Test Method</i>	<i>Result- Class</i>	<i>Standard</i>
Limited Oxygen Index (LOI)	28.7	ASTM D 2863
Horizontal	Class-0	UL 94/ ASTM D 635
Vertical	V-0	UL 94/ ASTM D 5048

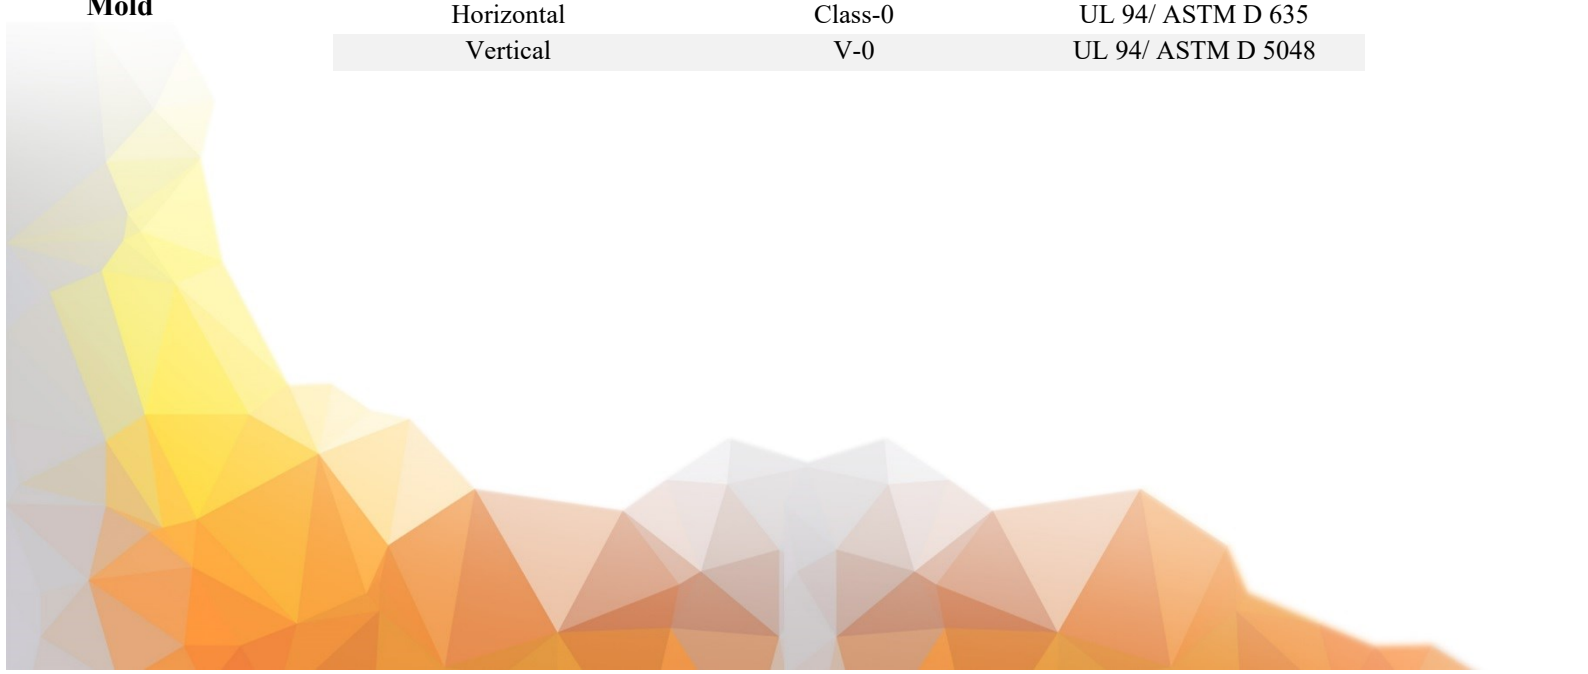

### Typical Casted Resin Properties<sup>3</sup>

<i>Property</i>	<i>Unit</i>	<i>Specification</i>	<i>Method</i>
Tensile Strength	MPa	Min 40	ISO 3268, ASTM D638, ISO 527-2&4
Elongation at Break	%	Min 1.0	ISO 3268, ASTM D638, ISO 527-2&4
Tensile Modulus	GPa	Min 3.0	ISO 3268, ASTM D638, ISO 527-2&4
Flexural Strength	MPa	Min 90	ISO 178/ASTM D 790
Flexural Modulus	GPa	Min 3.4	ISO 178/ASTM D 790
Heat Distortion Temperature	°C	Min 95	ISO 75
Barcol Hardness	Barcol	Min 48	ASTM D 2583
Water Absorption	%	Max 0.20	ISO 62- Test Method 3
Linear Shrinkage <sup>4</sup>	%	≈ 1.5	Internal method

- 3) Materials used for curing are: (Cobalt Octoate Farapol C 9010 1%- 1.0 phr, Akperox A60 1.0 phr). Curing Time is 24 hrs at Room Temperature and 3 hrs at 80 °C.  
 4) This test is done on the linear sample with dimensions (1 cm × 1 cm × 100 cm).

### Handling, Storage and Stability

FARAPOL O 136 is a product sensitive to temperature, Light, and oxidation. Hence, it should be stored indoors in a dry place at a temperature between 5 and 25 °C. Keep always in the original, unopened, and undamaged containers. Avoid keeping material exposed to sunlight. On storage under the conditions mentioned above, the shelf life for FARAPOL O 136 is 6 months.

### Healthy and Safety

Avoid storing the resin along with Metallic Driers and Peroxides in the same area. Safety Datasheets of the product are available on demand. The user is responsible to familiar with the material handling and safety datasheet before using the product.

### Packaging

Farapol O 136 is supplied in 200 Kg steel barrels and IBC tanks.

### Notice

The information contained herein is provided in good faith and is to the best of our knowledge accurate, but we assume no liability for its accuracy or completeness. Therefore, the buyer is advised to determine the suitability of this product for the intended use. We retain the right to make any changes according to technological progress or further developments.

### Document Registration

Pub. No: POL- F-76-33      Revision No.: 3      Rev. Date: 11/30/2023

### Contact Information

Tel: +98 21 26231019      Fax: +98 21 26231014  
 Site: [www.farapol.com](http://www.farapol.com)      Email: info@farapol.com

